

## **Original Research Article**

# **Improving the Photo-catalytic Efficiency of TiO<sub>2</sub> by incorporation of Cobalt For Removal of Micropollutants from Wastewater**

### **Abstract**

This work addresses the synthesis of Co-doped TiO<sub>2</sub> nanocrystals utilizing a single-step Solgel process and how the produced samples were used to photodegrade methylene blue MB. The crystal structure, including phase identification, crystalline size, texture, stress, and strain, has been verified by X-ray powder diffraction (XRD). The average crystallite size of nanocrystals decreased from 65.69 nm to 32.62 nm with the incorporation of 9% Co into the TiO<sub>2</sub> crystal lattice. The presence of Ti-O and C=O functional groups in the FTIR spectra shows the successful doping of Co. The optical band gap reduced from 3.39 eV for undoped TiO<sub>2</sub> to 3.06 eV for 9 % Co-doped TiO<sub>2</sub>, as confirmed by UV-Vis spectroscopy. The photocatalytic activity of the samples was studied utilizing the degradation of methylene blue as a model substance. Which was substantially increased from 5.86% for pure TiO<sub>2</sub> to 23.01% for Co-0.9%, with a rate constant of  $2.17 \times 10^{-3} \text{ min}^{-1}$ .

**Keywords:** Co-doped TiO<sub>2</sub> Nanocrystals ;Single step Sol-gel Method; photo-degradation; Methylene Blue dye, Wastewater

## 1. Introduction:

Metal oxide semiconductors, advanced functional materials such as two-component (alloyed), and metal-oxide nanoparticles have a significant impact on a range of applications in science and technology [1][2][3][4][5]. In recent decades, air and water pollution in urban areas produced mainly by automobiles and the chemical industry has become a serious threat to public health [6][7]. However, toxic organic compounds such as pesticides, dyes, phenols, and the associated environmental hazards are discharged into the aquatic environment through various anthropogenic inputs[8][2][9][10][11][12]. Despite their low concentration, the presence of these contaminants is still a major concern over public health and a major obstacle to water recycling due to their bio-recalcitrant and acute toxicity [13][14][15]. The method of “advanced oxidation processes” (AOPs) appears to become the focus of intense interest when the process can be driven by solar, UV, or visible light. Among AOPs,  $\text{TiO}_2$  is generally considered to be one of the important evergreen photocatalysts due to its desirable physical and chemical properties against photochemical corrosion, efficient photocatalytic activity, high photostability, low cost, and toxicity [16][17][18][9]. Photocatalysis involves activating a catalyst material with light energy to speed up chemical reactions. When a photocatalyst is exposed to light energy, the photons excite electrons in the valence band (VB) to the conduction band (CB), resulting in electron-hole pairs. The holes left over in the VB can react with adsorbed species like water or organic compounds, whereas, the excited electrons in the CB have a greater energy and can participate in different redox processes [19][20][12][21]. Titanium dioxide ( $\text{TiO}_2$ ) [22], zinc oxide ( $\text{ZnO}$ ) [23],  $\text{SnO}_2$  [24],  $\text{Fe}_2\text{O}_3$  [25],  $\text{CuO}$  [26], Co-doped  $\text{TiO}_2$  [27], and tungsten trioxide ( $\text{WO}_3$ ) [24] are a few metal oxide semiconductor (MOS) materials that have shown great promise as photocatalysts [28][29][24]. Among all of these MOS  $\text{TiO}_2$  has attained great significance in AOPs due to its remarkable features, including chemical and physical stability, non-toxicity, strong oxidative power, low cost, antibacterial activity, environmental friendliness, highly solar-activated surface, etc [30][31][32][33].  $\text{TiO}_2$  exists in three phases, anatase, rutile, and brookite,

of which anatase and rutile are known to be potentially active materials for many applications; such as in photocatalysis, water purification, solar cells, sensors, paints, etc. But the main drawback of these systems, for many of these applications, is their absorption in the UV region, which corresponds to only 3–5% of solar radiation [34][35][9]. However, the practical application of  $\text{TiO}_2$  is limited by two main factors. Firstly, only a small portion of the solar spectrum is absorbed in the ultraviolet UV light region due to the wide band gap nature of titania (3.2 eV) for anatase and (3.0 eV of rutile), secondly, the recombination rate of photogenerated electron-hole pairs is too high to be used for organic pollutant degradation in practice. Therefore  $\text{TiO}_2$  needs to attain photocatalytic response in a border range extending into visible light. To solve these difficulties, numerous researchers worked on titanium dioxide semiconductors utilizing different approaches to improve the photocatalytic performance of  $\text{TiO}_2$  [36]. *Toubal et al. (2017)* produced Co-doped  $\text{TiO}_2$  nanoparticles via sol gel synthesis and measured their electrical characteristics, finding that Co doping significantly increased  $\text{TiO}_2$  conductivity [27]. *Chanda et al (2021)* used the sol gel spin coating approach to create Co-doped  $\text{TiO}_2$  thin films, resulting in high refractive index  $\text{TiO}_2$  nano-films due to the integration of Co as a dopants material in the  $\text{TiO}_2$  lattice. Cobalt was chosen as a dopants material because, when exposed to UV light, Co- $\text{TiO}_2$  forms electron-hole pairs, which may subsequently combine with water molecules and oxygen in the air to create highly reactive oxygen species such as hydroxyl radicals ( $\text{OH}\bullet$ ) [37][38][39]. These radicals are powerful oxidants capable of breaking down organic pollutants and eliminating the microbiological contaminants found in wastewater. Currently, the most frequent preparation techniques include the gas phase process, hydrothermal method, sol-gel method, solvothermal method, and detonation method. Among the several synthesis processes the most prevalent is Solgel for material preparation. Sol-gel is one of the most utilized techniques; that is used mostly for creating thin films and nano powder photocatalysts. Many studies revealed that Solgel is a very simple technique, low temperature operatable, yielding large quantity of products, producing homogeneous materials with small

crystallite size and greater surface area which is the essential property for nano materials [40][20][41][42][43][44].

In the present work, we have prepared and characterized pure  $\text{TiO}_2$  and cobalt-doped  $\text{TiO}_2$  with 7% and 9% doping. The reduced crystallite size of the Co-doped  $\text{TiO}_2$  nanocrystals can change the shape of  $\text{TiO}_2$ , resulting in a higher surface-to-volume ratio and a greater number of active sites. Therefore, the photodegradation of methylene blue designated that the separation efficiency of the photogenerated electron and hole pairs was mainly improved due to Co-doping, and this led to a much greater photocatalytic activity for organic pollutant degradation. The relationship between the morphology, structure, optical properties, and photocatalytic activities of Co-doped  $\text{TiO}_2$  nanocrystals was investigated in detail [36].

## **2. Experimental Details**

### **2.1. Materials and Methods:**


All precursor ingredients, including titanium butoxide IV, cobalt sulfate, and aqueous HCl, were obtained from Sigma Aldrich (Germany), and ANALAR was used to prepare the undoped and Co-doped  $\text{TiO}_2$  nanoparticles utilizing a single-step sol-gel process. No further purification of the precursor materials was carried out; utilized as it is obtained from the seller.

#### **2.1.1 Preparation of Un-doped $\text{TiO}_2$**

The precursor Substance 10 mL of titanium butoxide (TBO) was added to with 20 mL of distilled water. After 20 minutes of constantly stirring at ambient temperature ( $27^\circ\text{C}$ ), 5 mL concentrated HCl was added dropwise to the solution, and steering was discontinued after 40 minutes. To make xerogel, the warmed samples were dried in an oven at  $150^\circ\text{C}$  for 12 hours. Bulk crystals then formed, indicating that the gel had entirely dried. The dried gel is crushed and pestled into fine powder. Calcination at  $500^\circ\text{C}$  for 4 hours was performed to eliminate any probable contaminants that degrade at high temperatures from the sample.

### 2.1.2 Preparation of Co-doped TiO<sub>2</sub> nanocrystals

Titanium butoxide (TBO) 10 mL was added to (0.7 g) Co(SO<sub>4</sub>), and after 20 minutes of constantly stirring at room temperature (27 °C), 20 mL filtered water and several drops of HCl were progressively put into the solution, and steering was stopped after 40 minutes. Warm samples were dried for 12 hours in a hot oven at 150 °C to produce xerogel. Due to the elimination of water, the dispersed gel shrank and became a viscous paste. Bulk crystals then formed, indicating that the gel was entirely dried. The dried gel was then ground into a fine powder with a mortar and pestle. To remove any suspicious impurities, Co-doped TiO<sub>2</sub> was calcined at 500 °C for 4 hours.

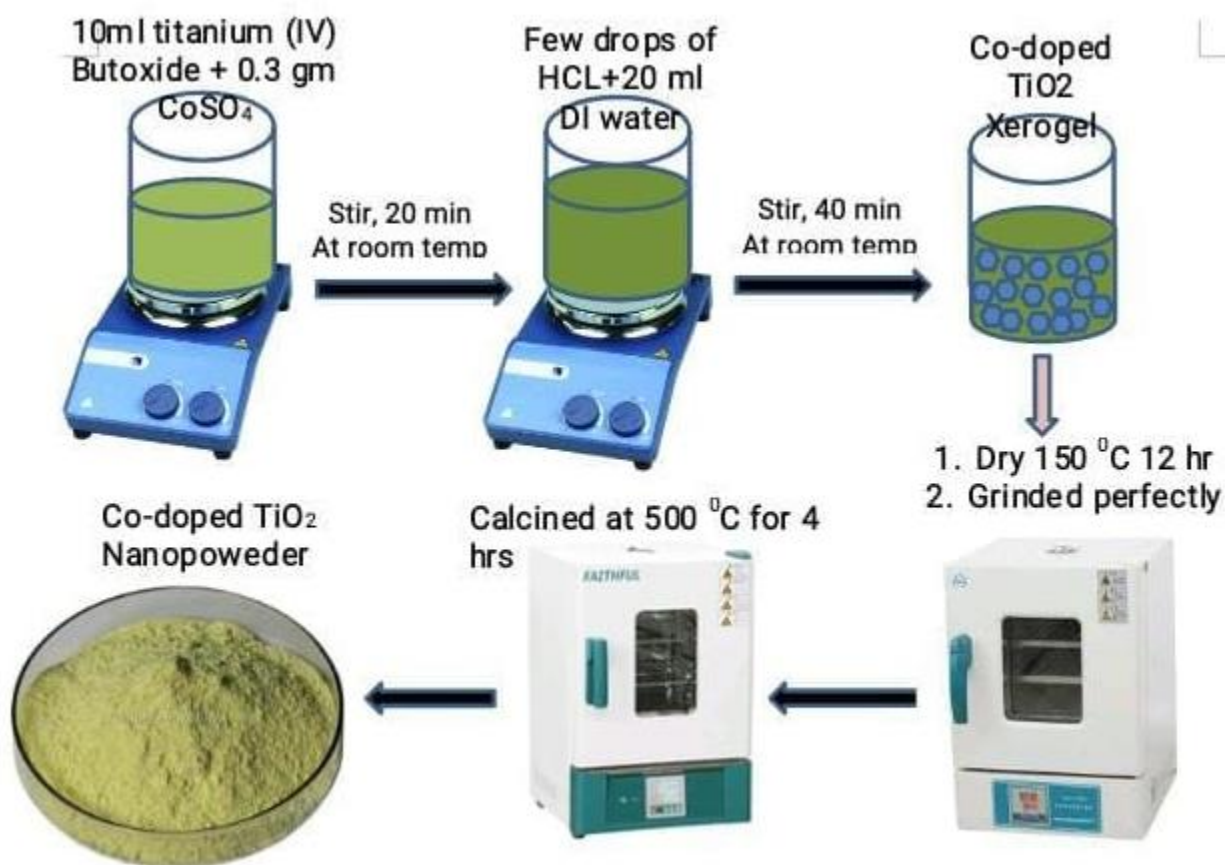

**Figure 1.** Schematic diagram of Single Step Sol-gel Synthesis of Co-doped TiO<sub>2</sub>

## 2.2. Photodegradation Activity of all prepared samples

The resulting nanocrystals were then exposed to direct sunshine, and the photodegradation rate using methylene blue (MB) at an initial dye amount of 10 mg per 500 ml was calculated for 1 mg of catalysts per 100 ml of dye mixture. To assess the samples' photocatalytic capability, the UV-vis absorption spectra were examined by exposing them to different periods of visible light. The available sunshine exposure period ranged from 0 to 120 minutes, with 15-minute intervals.

## 3. Results and Discussion


### 3.1. XRD Analysis:

Figure 2 shows the XRD spectra of all the synthesized samples. The highly intense and sharp peak round of about  $25^{\circ}$  observed in all samples confirms the anatase phase of  $\text{TiO}_2$  crystal. The sharp crystalline peaks were observed at 2 theta degrees  $25^{\circ}$ ,  $38^{\circ}$ ,  $48^{\circ}$ ,  $55^{\circ}$ ,  $56^{\circ}$ , and  $63^{\circ}$  respectively with respective (hkl) reflection planes (101), (004), (222), (200), (105) and (112). Furthermore, Co-doped  $\text{TiO}_2$  samples reveal mixed phases of  $\text{TiO}_2$  anatase as well as the rutile phase. It may be due to the incorporation of  $\text{Co}^{+2}$  ions can replace the  $\text{Ti}^{+4}$  ions in the  $\text{TiO}_2$  lattice which can create crystal defects owing to changes in their ionic radii and valence states. This deformation in the  $\text{TiO}_2$  crystal can alter the crystal structure, resulting in the simultaneous existence of anatase and rutile phases [45]. An extra peak observed at  $42.31^{\circ}$  in Co-doped  $\text{TiO}_2$  samples is due to Cobalt doping can change the phase stability of  $\text{TiO}_2$ , facilitating the transition from anatase to rutile. Co ions can reduce the energy barrier for this phase transition, resulting in the creation of an extra peak of the rutile phase. Scherrer equation (1) was used to determine the average crystallite size of all the samples.

$$D_{\text{ave}} = (0.94)\lambda / \beta \cos\theta \quad (1)$$

Here  $\theta$  is the diffraction angles,  $D$  is the average crystal size,  $\lambda$  is the corresponding incident wavelength of the diffraction X-ray exposure (1.5418 Å), and  $\beta$  is the full-width half maximum (FWHM) of the diffracted peaks. The average crystallite sizes ( $D$ ) for pure and Co-

doped (7% and 9%) TiO<sub>2</sub> nano-crystals were estimated as 34.52 nm, 32.62 nm, and 65.69 nm employing equation (1), which is also presented in Table 1. The inclusion of Co<sup>+2</sup> ions into the TiO<sub>2</sub> lattice resulted in a consistent drop in the crystallite size of the TiO<sub>2</sub> nanocrystals. Several other essential crystal characteristics, including microstrain, dislocation density, and crystallinity, have been measured and illustrated in Table 1. [46].

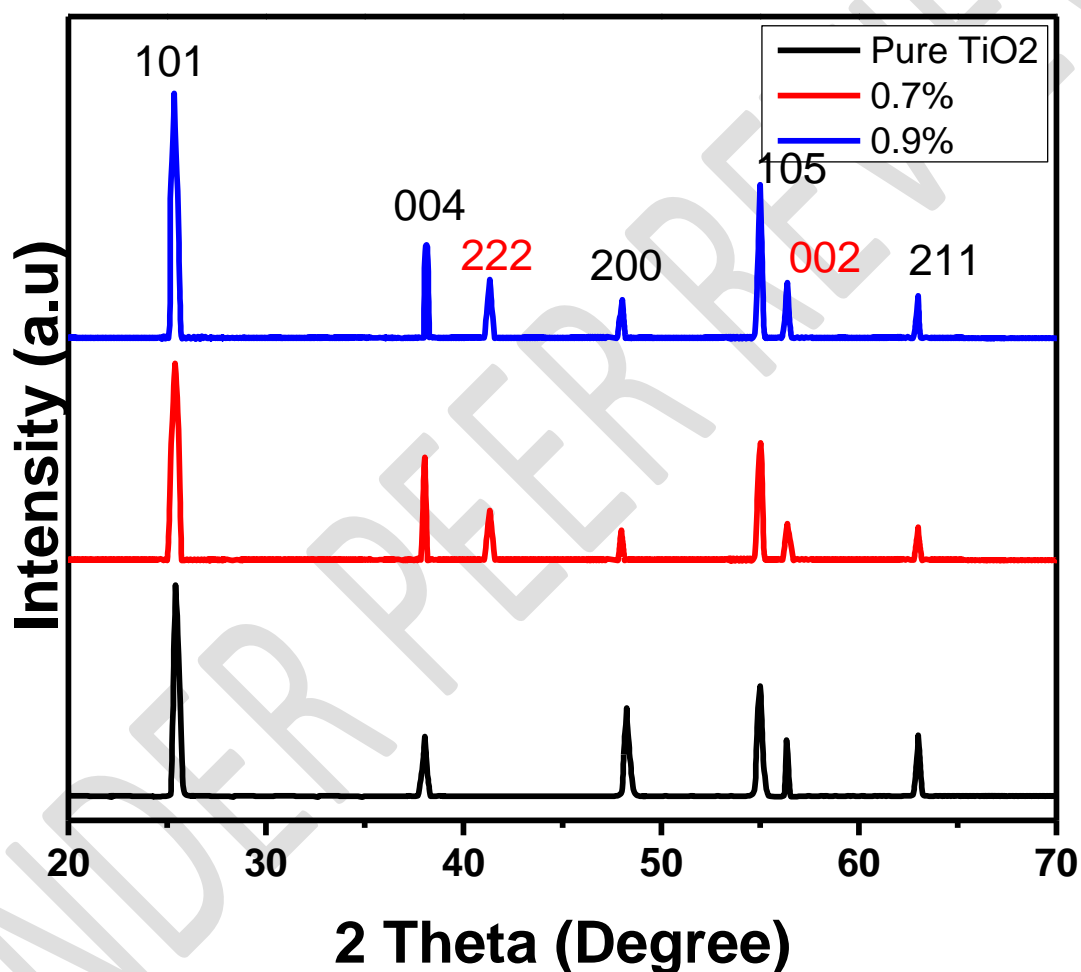

**Figure 2.** XRD Spectra of the pure and Co-doped TiO<sub>2</sub> nanocrystals

**Table: 1** Detailed photochemical properties of pure and Co-doped TiO<sub>2</sub> nanocrystals


Dopants Concentration	Crystallize sizes	Micro strain	Dislocation Density	Crystallinity	Eg
W%	(nm)	(10 <sup>-3</sup> )	(nm) <sup>-2</sup> x 10	%	(eV)

TiO <sub>2</sub> - Pure	65.69	0.584	0.8303	33.522	3.39
TiO <sub>2</sub> -Co 0.7 w%	34.52	0.492	1.5909	91.164	3.27
TiO <sub>2</sub> -Co 0.9 w%	32.62	0.415	1.544	55.53	3.06

### 3.2. FTIR Analysis:

Fourier Transform Infrared (FTIR) Spectra are commonly employed to explore the structure or function of a multi-component system [46]. The FTIR spectra of all synthesized samples pure and cobalt-doped TiO<sub>2</sub> NC's were observed in the wave number range of (4000 - 4000) cm<sup>-1</sup> as shown in Figure 3. Ti-O-Ti bonds are responsible for the sharp band observed in all samples about 421 cm<sup>-1</sup>. The broadband is caused by the dipole moment of nanocrystals around 1586 cm<sup>-1</sup> indicating the hydroxyl group of O-H stretching vibrations [36]. The peak at 2371 cm<sup>-1</sup> represents the asymmetric vibration (C=O) of CO<sub>2</sub> absorbed from the air during thermal treatment of titanium oxides [47]. The broad bands at 1759 cm<sup>-1</sup> and 3804 cm<sup>-1</sup> are attributed to stretching and bending vibrations of water molecules (H<sub>2</sub>O) that are adsorbed at the surface of the nanocrystals [48].



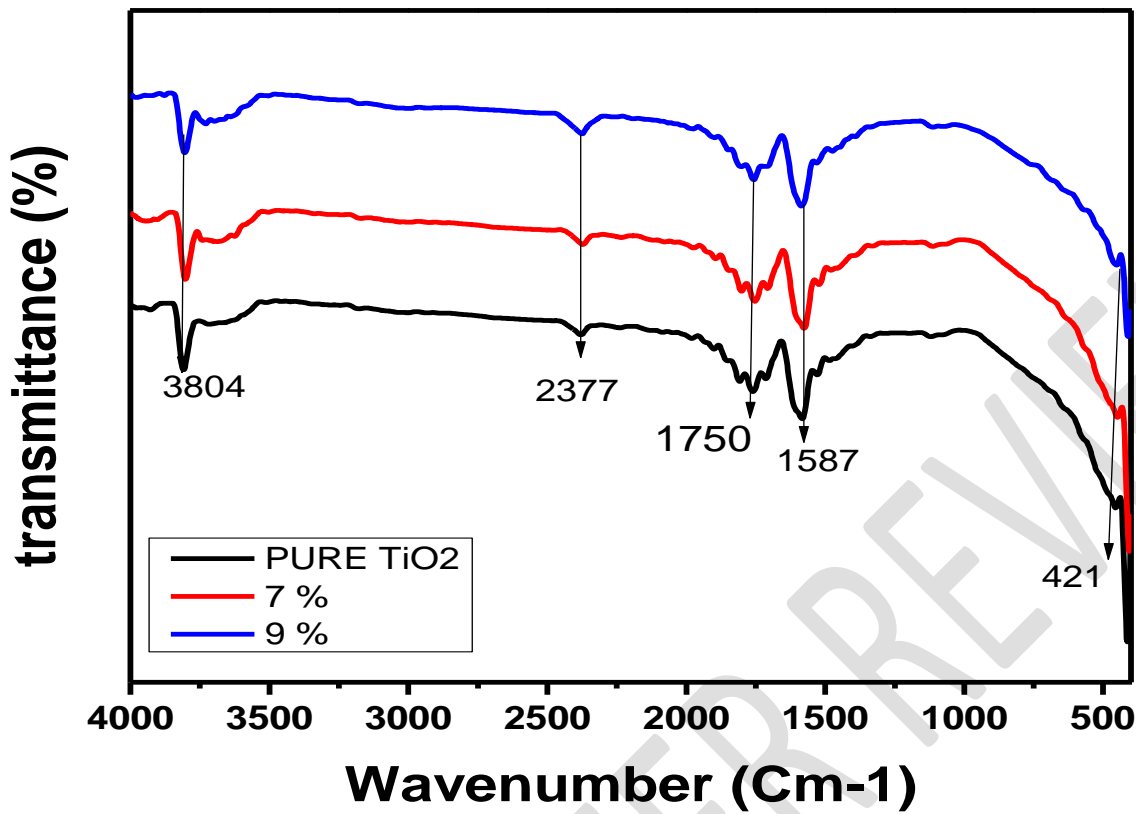

**Figure 3.** FTIR Spectra of the pure and Co-doped TiO<sub>2</sub> nanocrystals


### 3.3. UV Analysis:

Figure 4 depicts the UV-Vis absorbance spectra of all the produced samples, both pure and Co-doped TiO<sub>2</sub>, in the 200-800 nm region. The absorption edges of pure and different concentrations of Co-doped TiO<sub>2</sub> (0.7% and 9%) have been observed at 366, 379, and 405 nm, correspondingly. Figure 4 demonstrates that the absorption edge shifts towards longer wavelengths region while the percentage of Co enhances in the TiO<sub>2</sub> lattice structure indicating an alternate decline in the optical band gap of the TiO<sub>2</sub>. The indirect band gap transition was estimated using Equation 2.

$$(\alpha h\nu)^n = A(h\nu - E_g) \quad (2)$$

In the above equation,  $\alpha$  is the absorption coefficient calculated from UV data,  $h$  is the planks constant,  $n = 2$  for the indirect allowed transition and  $A$  represents the absorbance of the

material. The indirect optical band gap calculated values are 3.39 eV for pure  $\text{TiO}_2$ , 3.27 eV, and 3.06 eV for pure and 7% and 9% Co-doped  $\text{TiO}_2$  samples [39]. The declining behavior in optical band gap  $E_g$  is caused by the addition of  $\text{Co}^{+2}$  ions in  $\text{TiO}_2$ , which activates the nanocrystal material in the higher wavelength portion of the visible spectrum of light. It may be due to the development of new energy levels between the valance and conduction band of the  $\text{TiO}_2$  crystals caused by the inclusion of  $\text{Co}^{+2}$  ions.

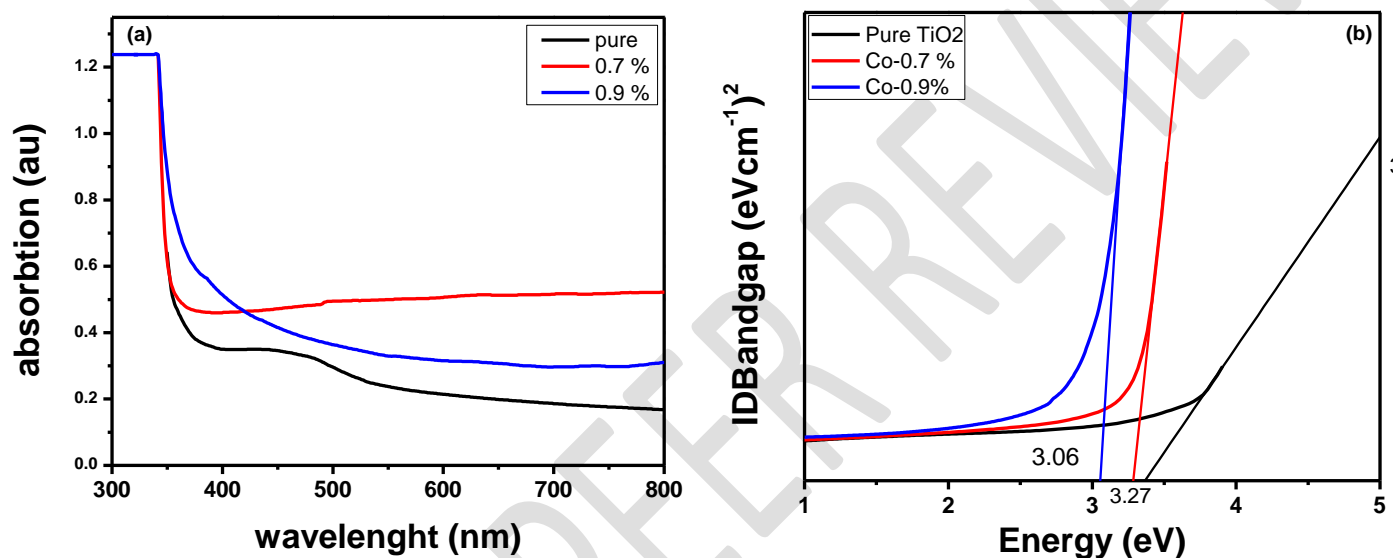

**Figure 4.** (a) UV visible absorbance spectra and (b) Indirect Bandgap Vs energy (eV) of the fabricated pure, 0.7 and 0.9 % Co-doped  $\text{TiO}_2$  nanocrystals


#### 4. Photocatalytic Activity


The produced nano-crystals were then exposed to direct sunshine, and the rate of photo-degradation using methylene blue (MB) at initial dye concentrations of 10 mg per 500 mL was calculated for 1 mg of catalysts per 100 mL of dye solution. To assess the samples' photocatalytic capacity, the UV-Vis absorption spectra were examined by exposing them to different periods of visible light. The available sunshine exposure period ranged from 0 to 120 minutes, with 15-minute intervals. A series of preliminary experiments were conducted to determine the influence of photocatalysis and adsorption on photocatalytic transformation. Photocatalysis studies were conducted at pH = 6 and a concentration of 1mg Co-doped  $\text{TiO}_2$  in

100 ml of MB solution [49]. It is observed that the methylene blue steadily degrades over time after each 15-minute interval under continuous exposure to sunlight. Figure 5 displays the findings of the photocatalytic decomposition of MB under visible sunlight in the presence of pure and Co-doped TiO<sub>2</sub> nanocrystals. Figure (5-a) reveals very minor degradation of MB (5.86 %) in the presence of pure TiO<sub>2</sub> nanocrystals during 120 min exposure to direct sunlight. The degradation of MB increases significantly up to 14.76 % and 23,01 % in the presence of 0.7 and 0.9 % Co-doped TiO<sub>2</sub> nanocrystals. Enhancing photodegradation of MB in the presence of Co-doped TiO<sub>2</sub> nanocrystals owing to Photocatalyst activity is determined by two primary factors: greater surface area and increased light absorption capacity in the visible spectrum [50]. The photodegradation efficiency of all produced nanocrystals was determined using the following equation:

$$\text{Photodegraded efficiency \%} = (C_0 - C_t / C_0) \times 100\% \quad (3)$$

Where  $C_0$  and  $C_t$  are before illumination and after MB degradation concentrations, respectively.[51]

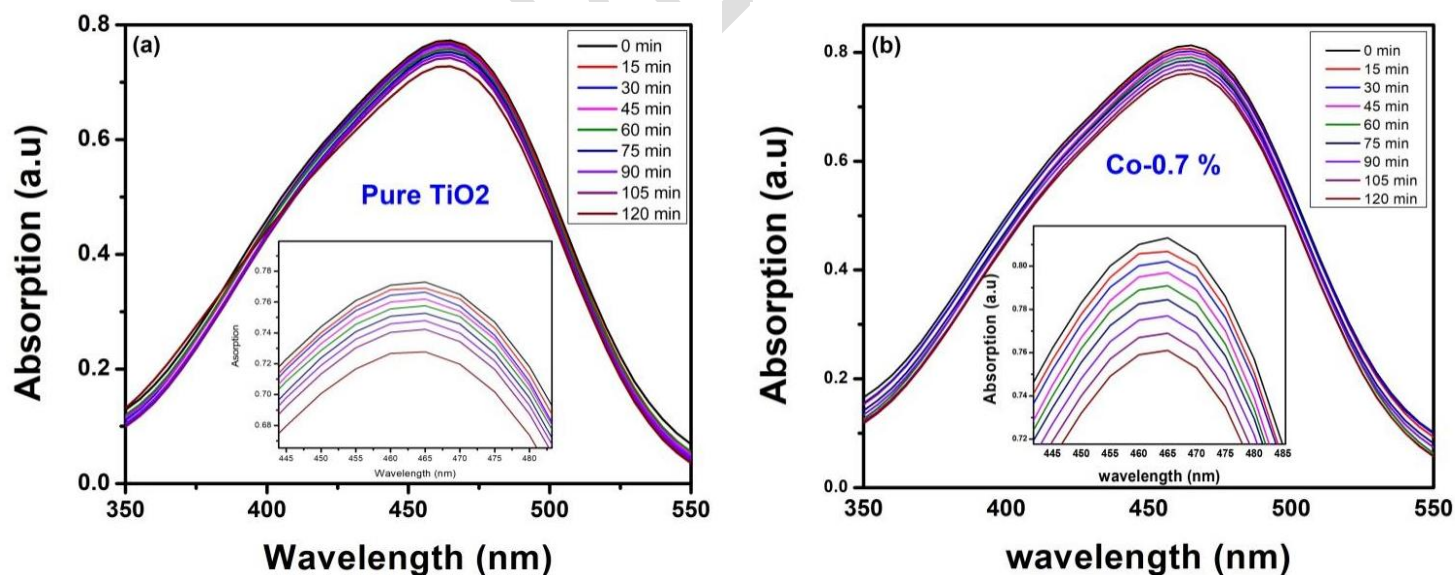

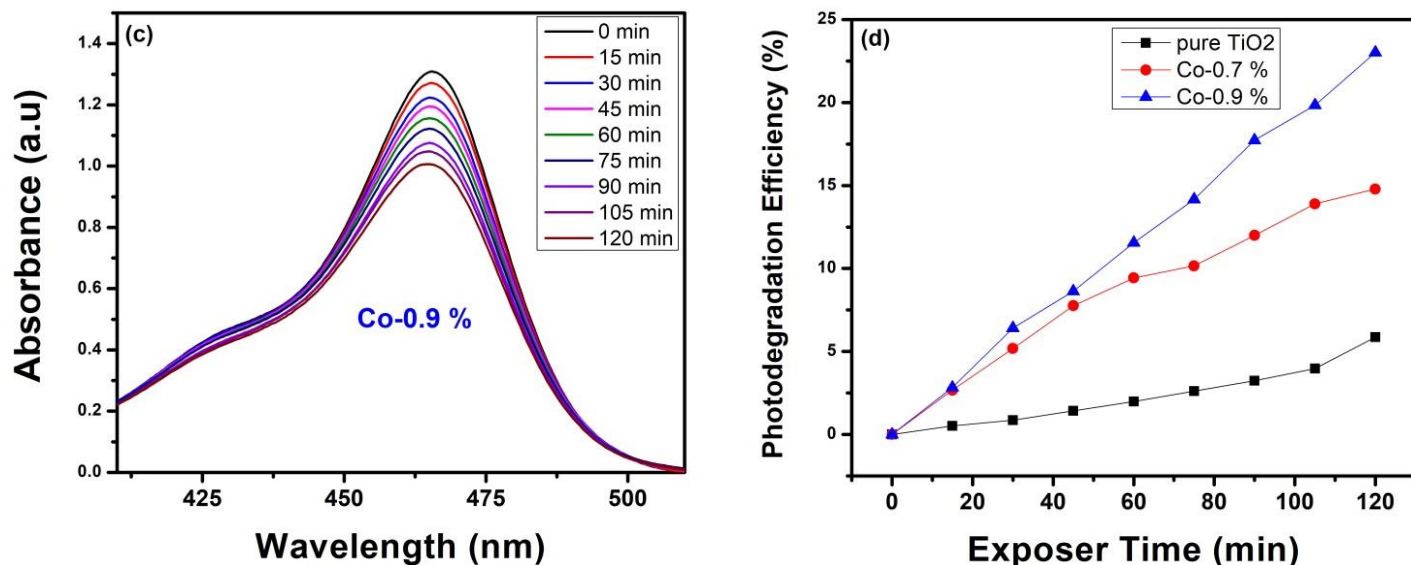

**Figure 5.** UV vis absorbance (a) Pure s (b) Co-0.7 % (c) Co-0.9 % (d) Photodegradation Efficiency Vs Exposer Time of all the fabricated samples


To further figure out how MB dye degrades photocatalytically, Figure 6 (a,b) displays the pseudo first-order model reaction kinetics of pure and, Co-doped TiO<sub>2</sub>. The dynamics of the first-order model are defined in Formula (4) below.

$$\ln C_0 / C_t = kt \quad (4)$$

Where  $C_0$  and  $C_t$  represent the amount of MB degraded in exposure to direct sunlight for a total of 120 minutes, divided into 15-minute intervals. The symbols  $t$  and  $k$  represent the reaction's time and rate constants, respectively. A tauc plot was used to analyze the linear fitting vs. irradiation time of MB photocatalytic degradation, as shown in Figure 6 (b). The projected kinetic degradation rate constant ( $k$ ) can be determined by studying the gradient of the fitting curve. Under direct sunlight, it was discovered that the estimated values of ( $k$ ) for pure TiO<sub>2</sub> and (0.7 & 0.9) % Co-doped TiO<sub>2</sub> are (0.45, 1.38, and 2.17)  $\times 10^{-3} \text{ min}^{-1}$ , as shown in Table 2. As shown in Figure (6-b) the rate constant for MB degradation increases with an increase in the concentration of the Co in TiO<sub>2</sub> nanocrystals and the half-life of decreases correspondingly.

**Table: 2.** Detailed photodegradation parameters of pure and Co-doped TiO<sub>2</sub> added MB

Dopant Concentration w%	Rate Constant k $\times 10^{-3} (\text{min}^{-1})$	Residual Concentration ( $R^2$ )	Half-life of Dye $t_{1/2} \times 10^{-3} (\text{min})$
Pure $\text{TiO}_2$	0.45	0.869	1.54
0.7 % Co- $\text{TiO}_2$	1.38	0.933	0.50
0.9 % Co- $\text{TiO}_2$	2.17	0.965	0.32

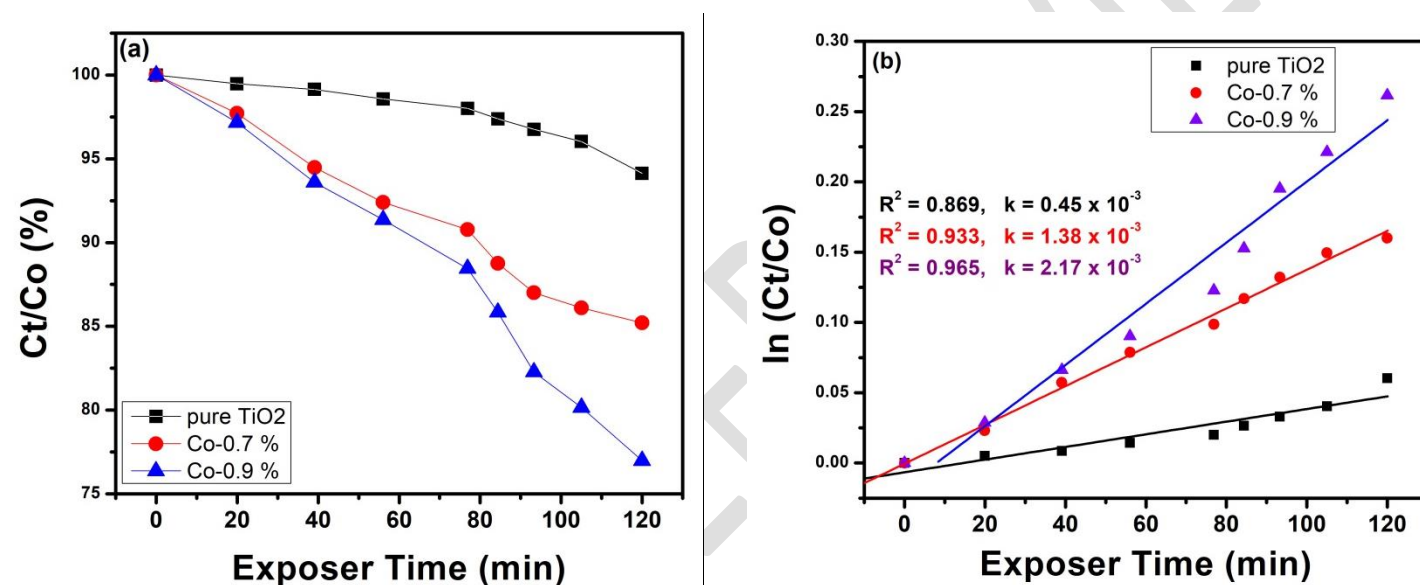



**Figure 6.** Pseudo First-order model reaction kinetics (a)  $C_t/C_0$  %, (b)  $\ln(C_t/C_0)$  pure, 0.7 % and 0.9 % Co-doped  $\text{TiO}_2$  nano-photocatalysts

#### 4.1. Photo-degradation Mechanism

When the MB solution is in the presence of fabricated nanocrystals subjected to direct sunlight, Co-doped  $\text{TiO}_2$  absorbs photons with energy equivalent to or exceeding its band gap. This energy stimulates electrons from the valence band (VB) to the conduction band (CB), resulting in electron-hole pairs ( $e^-$ ,  $h^+$ ).




Cobalt ions ( $\text{Co}^{+2}$ ) provide energy levels to the band gap of  $\text{TiO}_2$ . This lowers the band gap energy, allowing visible light to be absorbed while also improving electron-hole pair separation by capturing electrons or holes, lowering their recombination rate. Photogenerated electrons in the CB and holes in the VB undergo redox interactions with water ( $\text{H}_2\text{O}$ ) and oxygen ( $\text{O}_2$ ) molecules adsorbed on the  $\text{TiO}_2$  surface. These processes produce reactive oxygen species (ROS), such as hydroxyl radicals ( $\cdot\text{OH}$ ) and superoxide anions ( $\text{O}_2^-$ ).



The ROS produced in the earlier phase are highly reactive and can oxidize organic pollutants in MB dye, reducing them to smaller, less hazardous molecules like water and carbon dioxide.



Doping  $\text{TiO}_2$  with cobalt results in a change in  $\text{TiO}_2$ 's electronic arrangement. It is useful for aiding in the appropriate separation of electron-hole pairs and shifting light absorption to the visible range, hence boosting photocatalytic activity under sunlight. The use of a Co-doped  $\text{TiO}_2$  catalyst for photocatalytic degradation is extremely effective and can be reused multiple times without losing effectiveness. This makes it a sustainable solution for treating dye-contaminated water.

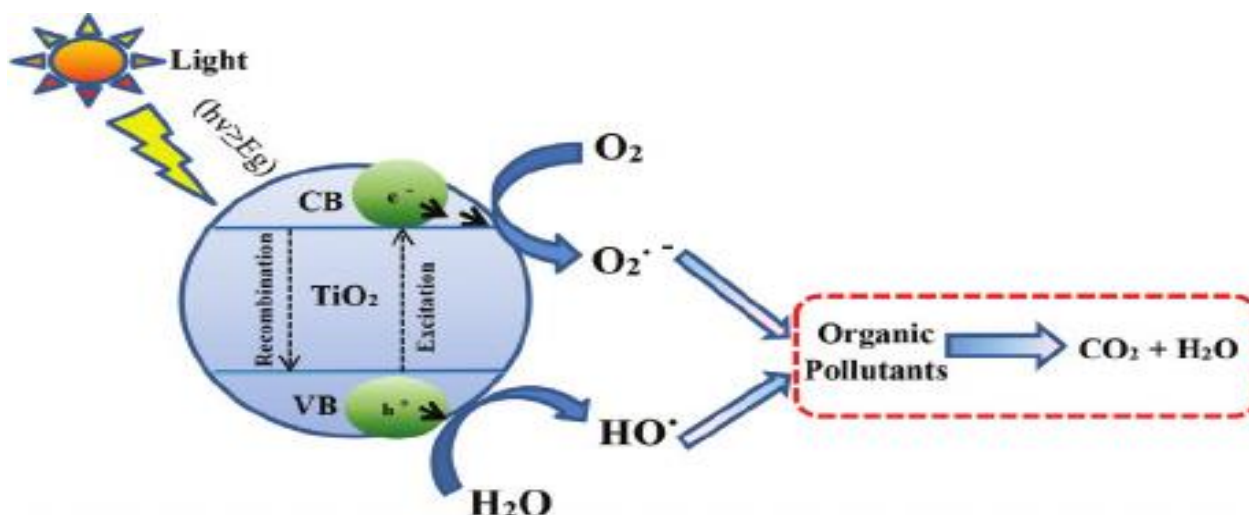

**Figure 7.** Schematic diagram of the photo-degradation of MB in the presence of Co-doped TiO<sub>2</sub> nanocrystals.

Table 3 presents a comparison of the current study to similar efforts in the literature. The current study outperforms several earlier publications.

**Table 3.** Comparison of current research with previous similar studies

Commercial Dye	Photocatalyst	Quantity	Degratation %	Exposer Time(min)	Reference
RB19	ZnO-KIL 2-1	800 mg/L	22	120	[52]
MB	Cu-TiO <sub>2</sub>	5 mg/L	17	120	[53]
MG	Cd-ZnO	500 mg/L	18	120	[54]
SMX	Co Doped TiO <sub>2</sub>	1.65 mg/L	9.88	120	[55]
MB	Co-TiO <sub>2</sub>	1 mg/L	23.01	120	Current study

## 5. Conclusion

A single-step Sol-gel synthesis technique was used to successfully produce Co-doped TiO<sub>2</sub> nanocrystals, which were then used to degrade MB, a commercial dye widely used in the cotton and paint industries. The synthesized nanocrystals were characterized through various material



characterization techniques such as XRD, FTIR, and UV which confirm the successful doping of Cobalt into TiO<sub>2</sub> lattice with enhanced photocatalytic and optical properties. The increase in the Cobalt concentration in the TiO<sub>2</sub> crystal lattice reveals a gradual increase in the photodegradation of MB and also results in the reduction of the band gap energies of the TiO<sub>2</sub> nanocrystals. Overall Co-doped TiO<sub>2</sub> has stronger photocatalytic activity than pure TiO<sub>2</sub> due to improved light absorption, charge separation, ROS production, stability, and reusability. Future research should focus on developing better synthesis methods to control the size, shape, and dispersion of Co-doped TiO<sub>2</sub> nanocrystals, resulting in improved photocatalytic capabilities.

### **List of Abbrivations**

XRD (X-ray powder diffraction)

FTIR (Fourier Transform Infrared Spectroscopy)

UV (Ultraviolet)

Co (cobalt)

AOPs (Advanced Oxidation Processes)

CB (conduction band)

VB (valance band)

TiO<sub>2</sub> (titanium dioxide)

MB (methylene blue)

Cr (chromium)

E<sub>g</sub> (band gap energy)

α (absorbtion coefficient)



h (planks constant)

TBO (titanium butoxide)

mL (milli litre)

k (rate constant)

### **Data Availability Statement:**

The datasets generated and analyzed during the current study are available from the corresponding author on reasonable request.

### **Diclaration of Intrest**

☒ The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

### **References**

- [1] M. Irfan *et al.*, “Improving photocatalytic efficiency of ZnO nanoflowers through gold incorporation for Rhodamine B photodegradation,” *Opt. Mater. (Amst)*., vol. 154, p. 115681, Aug. 2024, doi: 10.1016/j.optmat.2024.115681.
- [2] M. S. Chavali and M. P. Nikolova, “Metal oxide nanoparticles and their applications in nanotechnology,” *SN Applied Sciences*, vol. 1, no. 6. Springer Nature, Jun. 01, 2019. doi: 10.1007/s42452-019-0592-3.
- [3] J. Maragatha, S. Rajendran, T. Endo, and S. Karuppuchamy, “Microwave synthesis of metal doped TiO<sub>2</sub> for photocatalytic applications,” *J. Mater. Sci. Mater. Electron.*, vol. 28, no. 7, pp. 5281–5287, Apr. 2017, doi: 10.1007/s10854-016-6185-7.
- [4] Y. Deng, “Sensing Mechanism and Evaluation Criteria of Semiconducting Metal Oxides Gas Sensors,” in *Semiconducting Metal Oxides for Gas Sensing*, Springer Singapore, 2019,

pp. 23–51. doi: 10.1007/978-981-13-5853-1\_2.

- [5] K. G. Krishna, S. Parne, N. Pothukanuri, V. Kathirvelu, S. Gandhi, and D. Joshi, “Nanostructured metal oxide semiconductor-based gas sensors: A comprehensive review,” *Sensors and Actuators A: Physical*, vol. 341. Elsevier B.V., Jul. 01, 2022. doi: 10.1016/j.sna.2022.113578.
- [6] M. Aqeel, M. Ikram, M. Imran, and A. Ul-hamid, “TiO<sub>2</sub> Co-doped with Zr and Ag shows highly suitable for treatment of polluted water,” vol. 2, pp. 42235–42248, 2020, doi: 10.1039/d0ra08718a.
- [7] Y. Zhao *et al.*, “Rapid proton exchange between surface bridging hydroxyls and adsorbed molecules on TiO<sub>2</sub>,” *Appl. Catal. B Environ.*, vol. 277, p. 119234, 2020, doi: 10.1016/j.apcatb.2020.119234.
- [8] A. Kononov *et al.*, “Online breath analysis using metal oxide semiconductor sensors (electronic nose) for diagnosis of lung cancer,” *J. Breath Res.*, vol. 14, no. 1, 2020, doi: 10.1088/1752-7163/ab433d.
- [9] A. H. Navidpour, S. Abbasi, D. Li, A. Mojiri, and J. L. Zhou, “Investigation of Advanced Oxidation Process in the Presence of TiO<sub>2</sub> Semiconductor as Photocatalyst: Property, Principle, Kinetic Analysis, and Photocatalytic Activity,” *Catalysts*, vol. 13, no. 2, p. 232, Jan. 2023, doi: 10.3390/catal13020232.
- [10] V. Soni, A. N. Singh, P. Singh, and A. Gupta, “Photocatalytic dye-degradation activity of nano-crystalline Ti<sub>1-x</sub>M<sub>x</sub>O<sub>2-δ</sub> (M = Ag, Pd, Fe, Ni and x = 0, 0.01) for water pollution abatement,” *RSC Adv.*, vol. 12, no. 29, pp. 18794–18805, 2022, doi: 10.1039/d2ra02847f.
- [11] R. Mohammed, M. E. M. Ali, E. Gomaa, and M. Mohsen, “Green ZnO nanorod material for dye degradation and detoxification of pharmaceutical wastes in water,” *J. Environ. Chem. Eng.*, vol. 8, no. 5, p. 104295, 2020, doi: 10.1016/j.jece.2020.104295.
- [12] N. Verma *et al.*, “Characterization of Fabricated Gold-Doped ZnO Nanospheres and Their Use as a Photocatalyst in the Degradation of DR-31 Dye,” *J. Nanomater.*, vol. 2022, 2022, doi: 10.1155/2022/7532332.

- [13] M. Irfan, M. I. Khan, M. Al Huwayz, and N. Alwadai, "Synthesis, characterization, and photodegradation assessment of Ni and Cd-doped TiO<sub>2</sub> nanocrystals via sol-gel method for methylene blue under sunlight," *Dig. J. Nanomater. Biostructures*, vol. 19, no. 2, pp. 953–966, 2024, doi: 10.15251/DJNB.2024.192.953.
- [14] W. K. Jo, Y. G. Kim, and S. Tonda, "Hierarchical flower-like NiAl-layered double hydroxide microspheres encapsulated with black Cu-doped TiO<sub>2</sub> nanoparticles: Highly efficient visible-light-driven composite photocatalysts for environmental remediation," *J. Hazard. Mater.*, vol. 357, pp. 19–29, Sep. 2018, doi: 10.1016/j.jhazmat.2018.05.038.
- [15] A. Samadi *et al.*, "Stratum corneum hydration in healthy adult humans according to the skin area, age and sex: a systematic review and meta-analysis," *J. Eur. Acad. Dermatology Venereol.*, vol. 36, no. 10, pp. 1713–1721, Oct. 2022, doi: 10.1111/jdv.18297.
- [16] Z. Yang, L. Qin, P. Tian, and Y. Zhang, "Review of N and Metal co-Doped TiO<sub>2</sub> for Water Purification under Visible Light Irradiation 2 . Principle of Photocatalytic Oxidation Process," vol. 78, pp. 31–40, 2014, doi: 10.7763/PCBEE.
- [17] Y. Chen, D. Zeng, K. Zhang, A. Lu, L. Wang, and D.-L. Peng, "Au–ZnO hybrid nanoflowers, nanomultipods and nanopyramids: one-pot reaction synthesis and photocatalytic properties," *Nanoscale*, vol. 6, no. 2, pp. 874–881, 2014, doi: 10.1039/C3NR04558G.
- [18] D. E. Juárez-Cortazar *et al.*, "Doping of TiO<sub>2</sub> Using Metal Waste (Door Key) to Improve Its Photocatalytic Efficiency in the Mineralization of an Emerging Contaminant in an Aqueous Environment," *Water*, vol. 14, no. 9, p. 1389, Apr. 2022, doi: 10.3390/w14091389.
- [19] S. Challagulla, K. Tarafder, R. Ganesan, and S. Roy, "Structure sensitive photocatalytic reduction of nitroarenes over TiO<sub>2</sub>," *Sci. Rep.*, vol. 7, no. 1, p. 8783, Aug. 2017, doi: 10.1038/s41598-017-08599-2.
- [20] A. Khlyustova, N. Sirotkin, T. Kusova, A. Kraev, V. Titov, and A. Agafonov, "Doped TiO<sub>2</sub>: The effect of doping elements on photocatalytic activity," *Mater. Adv.*, vol. 1, no. 5,

pp. 1193–1201, 2020, doi: 10.1039/d0ma00171f.

- [21] S. F. Lee, E. Jimenez-Relinque, I. Martinez, and M. Castellote, “Effects of Mott–Schottky Frequency Selection and Other Controlling Factors on Flat-Band Potential and Band-Edge Position Determination of TiO<sub>2</sub>,” *Catalysts*, vol. 13, no. 6, p. 1000, Jun. 2023, doi: 10.3390/catal13061000.
- [22] J. Tomić and N. Malinović, “Titanium dioxide photocatalyst: Present situation and future approaches,” *AIDASCO Rev.*, vol. 1, no. 2, pp. 26–30, Jun. 2023, doi: 10.59783/aire.2023.27.
- [23] S. Modi *et al.*, “Photocatalytic Degradation of Methylene Blue Dye from Wastewater by Using Doped Zinc Oxide Nanoparticles,” *Water*, vol. 15, no. 12, p. 2275, Jun. 2023, doi: 10.3390/w15122275.
- [24] Q. Li, W. Zeng, and Y. Li, “Metal oxide gas sensors for detecting NO<sub>2</sub> in industrial exhaust gas: Recent developments,” *Sensors and Actuators B: Chemical*, vol. 359. Elsevier B.V., May 15, 2022. doi: 10.1016/j.snb.2022.131579.
- [25] T. J. Al-Musawi *et al.*, “Degradation of amoxicillin under a UV or visible light photocatalytic treatment process using Fe<sub>2</sub>O<sub>3</sub>/bentonite/TiO<sub>2</sub>: Performance, kinetic, degradation pathway, energy consumption, and toxicology studies,” *Optik (Stuttg.)*, vol. 272, p. 170230, Feb. 2023, doi: 10.1016/j.ijleo.2022.170230.
- [26] F. Ullah, U. Ghani, and M. S. Mohamed Saheed, “A PN-type CuO@TiO<sub>2</sub> nanorods heterojunction for efficient PEC water splitting: DFT model and experimental investigation on the effect of calcination temperature,” *Int. J. Hydrogen Energy*, Aug. 2023, doi: 10.1016/j.ijhydene.2023.07.159.
- [27] B. Toubal, R. Bensaha, and F. Yakuphanoglu, “The influence of copper-cobalt co-doping on optical and electrical properties of nanostructures TiO<sub>2</sub> thin films prepared by sol-gel,” *J. Sol-Gel Sci. Technol.*, vol. 82, no. 2, pp. 478–489, 2017, doi: 10.1007/s10971-017-4337-8.
- [28] A. U. Hasanah, P. L. Gareso, N. Rauf, and D. Tahir, “Photocatalytic Performance of Zinc

Oxide and Metal-Doped Zinc Oxide for Various Organic Pollutants,” *ChemBioEng Rev.*, vol. 10, no. 5, pp. 698–710, Oct. 2023, doi: 10.1002/cben.202300004.

- [29] X. Gao and T. Zhang, “An overview: Facet-dependent metal oxide semiconductor gas sensors,” *Sensors and Actuators, B: Chemical*, vol. 277. Elsevier B.V., pp. 604–633, Dec. 20, 2018. doi: 10.1016/j.snb.2018.08.129.
- [30] M. Patricia, B. Vega, M. H. Aracely, H. J. Luis, G. Mar, and V. R. L. Hinojosa-reyes, “Visible light photocatalytic activity of sol – gel Ni-doped TiO<sub>2</sub> on p - arsanilic acid degradation,” *J. Sol-Gel Sci. Technol.*, 2018, doi: 10.1007/s10971-018-4579-0.
- [31] M. Trzeciak, P. Miądlicki, and B. Tryba, “Enhanced Degradation of Ethylene in Thermo-Photocatalytic Process Using TiO<sub>2</sub> / Nickel Foam : Reaction Mechanism,” 2023, doi: 10.20944/preprints202311.1352.v1.
- [32] C. Chambers, S. B. Stewart, B. Su, H. F. Jenkinson, J. R. Sandy, and A. J. Ireland, “Silver doped titanium dioxide nanoparticles as antimicrobial additives to dental polymers,” *Dent. Mater.*, vol. 33, no. 3, pp. e115–e123, Mar. 2017, doi: 10.1016/j.dental.2016.11.008.
- [33] J. Bahadur, S. Agrawal, A. Parveen, A. Jawad, S. S. Z. Ashraf, and R. M. Ghalib, “Micro-Structural, Optical and Dielectric Properties of Ag Doped TiO<sub>2</sub> Synthesized by Sol–Gel Method,” *Mater. Focus*, vol. 4, no. 2, pp. 134–141, Jul. 2015, doi: 10.1166/mat.2015.1228.
- [34] B. Choudhury and A. Choudhury, “Luminescence characteristics of cobalt doped TiO<sub>2</sub> nanoparticles,” vol. 132, pp. 178–184, 2012, doi: 10.1016/j.jlumin.2011.08.020.
- [35] G. Y. Nigussie *et al.*, “Antibacterial activity of Ag-Doped TiO<sub>2</sub> and Ag-Doped ZnO nanoparticles,” *Int. J. Photoenergy*, vol. 2018, 2018, doi: 10.1155/2018/5927485.
- [36] B. Singaram, J. Jeyaram, R. Rajendran, and P. Arumugam, “Visible light photocatalytic activity of tungsten and fluorine codoped TiO<sub>2</sub> nanoparticle for an efficient dye degradation,” 2018.
- [37] K. R. Anju, R. Thankapan, J. R. Rajabathar, and H. A. Al-Lohedan, “Hydrothermal synthesis of nanosized (Fe, Co, Ni)-TiO<sub>2</sub> for enhanced visible light photosensitive

applications,” *Optik (Stuttg)*., vol. 165, no. 2010, pp. 408–415, 2018, doi: 10.1016/j.ijleo.2018.03.091.

- [38] Y. Essam and G. H. El-Nowihy, “N-Co-Cd-doped TiO<sub>2</sub> nanocomposite for efficient dye-synthesized solar cells,” *Ain Shams Eng. J.*, p. 102180, Jan. 2023, doi: 10.1016/j.asej.2023.102180.
- [39] S. A. Mansour, A. H. Farha, and M. F. Kotkata, “Sol–gel Synthesized Co-Doped Anatase TiO<sub>2</sub> Nanoparticles: Structural, Optical, and Magnetic Characterization,” *J. Inorg. Organomet. Polym. Mater.*, vol. 29, no. 4, pp. 1375–1382, 2019, doi: 10.1007/s10904-019-01102-6.
- [40] U. G. Akpan and B. H. Hameed, “Applied Catalysis A : General The advancements in sol – gel method of doped-TiO<sub>2</sub> photocatalysts,” vol. 375, pp. 1–11, 2010, doi: 10.1016/j.apcata.2009.12.023.
- [41] Y. Wang, H. Cheng, Y. Hao, J. Ma, W. Li, and S. Cai, “Photoelectrochemical properties of metal-ion-doped TiO<sub>2</sub> nanocrystalline electrodes.”
- [42] K. I. Dhanalekshmi, P. Magesan, M. J. Umapathy, X. Zhang, N. Srinivasan, and K. Jayamoorthy, “Enhanced photocatalytic and photodynamic activity of chitosan and garlic loaded CdO–TiO<sub>2</sub> hybrid bionanomaterials,” *Sci. Rep.*, vol. 11, no. 1, p. 20790, Oct. 2021, doi: 10.1038/s41598-021-00242-5.
- [43] A. Ranjitha, N. Muthukumarasamy, M. Thambidurai, and D. Velauthapillai, “Enhanced photovoltaic performance of quantum dot sensitized solar cells with Ag-doped TiO<sub>2</sub> nanocrystalline thin films,” *J. Mater. Sci. Mater. Electron.*, vol. 25, no. 6, pp. 2724–2729, 2014, doi: 10.1007/s10854-014-1935-x.
- [44] M. Kunnamareddy, R. Rajendran, M. Sivagnanam, R. Rajendran, and B. Diravidamani, “Nickel and sulfur codoped TiO<sub>2</sub> nanoparticles for efficient visible light photocatalytic activity,” *J. Inorg. Organomet. Polym. Mater.*, vol. 31, no. 6, pp. 2615–2626, Jun. 2021, doi: 10.1007/s10904-021-01914-5.
- [45] S. Douven *et al.*, “Cost-Effective Visible LED Light : From Powders to Films,” no. x.

- [46] M. N. Kiani *et al.*, “Synthesis and Characterization of Cobalt-Doped Ferrites for Biomedical Applications,” pp. 2–8, 2023, doi: 10.1021/acsomega.2c05226.
- [47] N. Naveen, “Investigation on physiochemical properties of Mn substituted spinel cobalt oxide for supercapacitor applications,” no. July, 2019, doi: 10.1016/j.electacta.2014.01.161.
- [48] A. El Mragui, O. Zegaoui, I. Daou, and J. C. G. Esteves da Silva, “Preparation, characterization, and photocatalytic activity under UV and visible light of Co, Mn, and Ni mono-doped and (P,Mo) and (P,W) co-doped TiO<sub>2</sub> nanoparticles: a comparative study,” *Environ. Sci. Pollut. Res.*, vol. 28, no. 20, pp. 25130–25145, 2021, doi: 10.1007/s11356-019-04754-6.
- [49] A. Garg *et al.*, “Photocatalytic Degradation of Bisphenol-A using N, Co Codoped TiO<sub>2</sub> Catalyst under Solar Light,” *Sci. Rep.*, vol. 9, no. 1, pp. 1–13, 2019, doi: 10.1038/s41598-018-38358-w.
- [50] A. E. Pirbazari, P. Monazzam, and B. F. Kisomi, “Co/TiO<sub>2</sub> nanoparticles: Preparation, characterization and its application for photocatalytic degradation of methylene blue,” *Desalin. Water Treat.*, vol. 63, pp. 283–292, 2017, doi: 10.5004/dwt.2017.20205.
- [51] M. Aqeel *et al.*, “TiO<sub>2</sub>Co-doped with Zr and Ag shows highly efficient visible light photocatalytic behavior suitable for treatment of polluted water,” *RSC Adv.*, vol. 10, no. 69, pp. 42235–42248, 2020, doi: 10.1039/d0ra08718a.
- [52] D. Maučec, A. Šuligoj, A. Ristić, G. Dražić, A. Pintar, and N. N. Tušar, “Titania versus zinc oxide nanoparticles on mesoporous silica supports as photocatalysts for removal of dyes from wastewater at neutral pH,” *Catal. Today*, vol. 310, no. February, pp. 32–41, 2018, doi: 10.1016/j.cattod.2017.05.061.
- [53] K. H. Lee *et al.*, “The Comparison of Metal Doped TiO<sub>2</sub> Photocatalytic Active Fabrics under Sunlight for Waste Water Treatment Applications,” *Catalysts*, vol. 13, no. 9, p. 1293, Sep. 2023, doi: 10.3390/catal13091293.
- [54] A. Phuruangrat, S. Mad-Ahin, O. Yayapao, S. Thongtem, and T. Thongtem,

“Photocatalytic degradation of organic dyes by UV light, catalyzed by nanostructured Cd-doped ZnO synthesized by a sonochemical method,” *Res. Chem. Intermed.*, vol. 41, no. 12, pp. 9757–9772, 2015, doi: 10.1007/s11164-015-1963-z.

- [55] M. Jahdi, S. B. Mishra, E. N. Nxumalo, S. D. Mhlanga, and A. K. Mishra, “Smart pathways for the photocatalytic degradation of sulfamethoxazole drug using F-Pd co-doped TiO<sub>2</sub> nanocomposites,” *Appl. Catal. B Environ.*, vol. 267, no. October 2019, p. 118716, 2020, doi: 10.1016/j.apcatb.2020.118716.